



DE - Brand:

## Special Steel

# CP72

### Chemical composition: (Typical analysis in %)

C	Cr	Mo	V	W			
1,10	7,50	1,50	2,10	1,10			

### Steel properties:

Cold work steel, high vanadium and tungsten, very good secondary hardness, good toughness, minimal size changes.

### Applications:

Cutting tools, bending tools, pressure- profile rolls, thread rolling dies, stamping tools.

### Condition of delivery:

Soft annealed to max. 250 HB

### Physical properties:

Thermal expansion coefficient	$\left[ \frac{10^{-6} \cdot \text{m}}{\text{m} \cdot \text{K}} \right]$	$\frac{20-100^{\circ}\text{C}}{11,4}$	$\frac{20-200^{\circ}\text{C}}{11,7}$	$\frac{20-300^{\circ}\text{C}}{12,1}$	$\frac{20-400^{\circ}\text{C}}{12,3}$
Thermal conductivity	$\left[ \frac{\text{W}}{\text{m} \cdot \text{K}} \right]$	$\frac{20^{\circ}\text{C}}{24,8}$			

### Heat treatment:

Soft annealing

Temperature	Cooling	Hardness
800 - 840°C	furnace	max. 250 HB


Stress relief annealing

Temperature	Cooling	
600 - 650°C	furnace	


Hardening

Temperature	Cooling	Tempering
1120 - 1140°C	oil, pressure gas (N <sub>2</sub> ), air or hot bath 500 - 550°C	see tempering diagram


## (CP72) Thermal Cycle Diagram

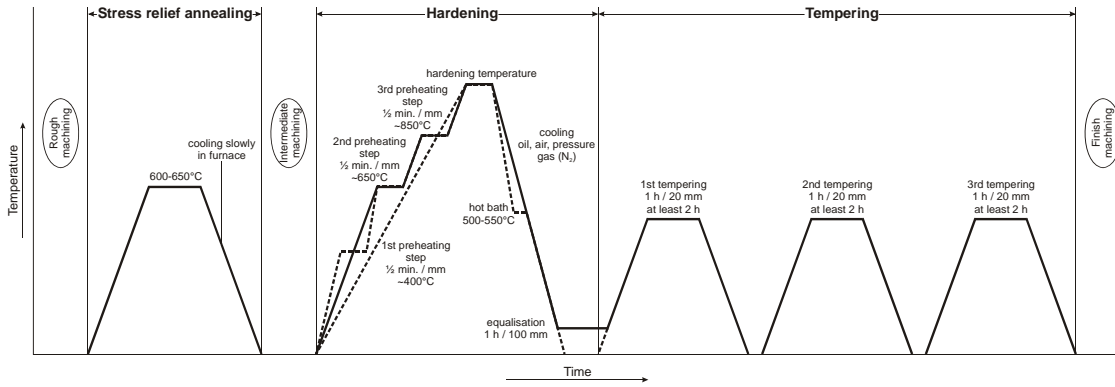

## Continuous Cooling Transformation Diagram (CCT)

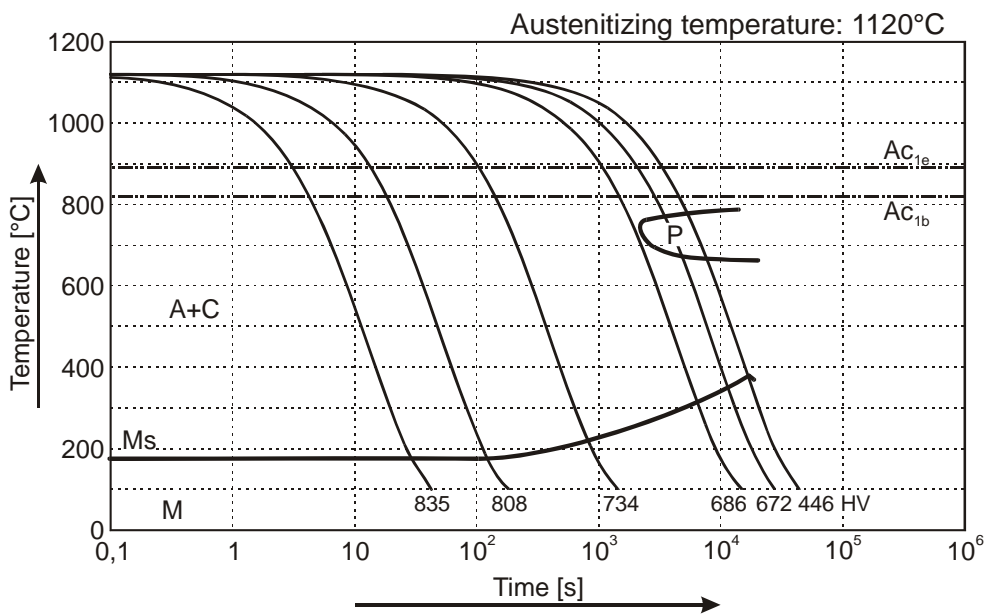

## Tempering Diagram

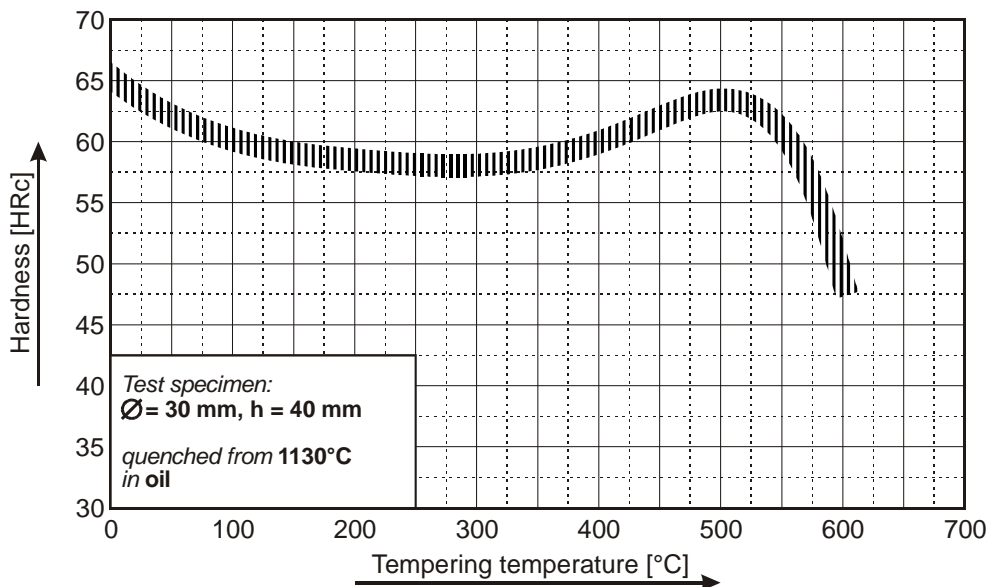

Remarks: All technical information is for reference only.